

SR GreenPoxy 33 / SZ 8525

Clear epoxy system for compression moulding

High bio-based carbon content



SR GreenPoxy 33 resin is outcoming from the latest innovations in bio-based chemistry.
SR GreenPoxy 33 resin is produced with a high content of carbon from plant origin.
The bio-based Carbon content of our system is certified by an independent laboratory using Carbon 14 measurements (ASTM D6866 or XP CEN/TS 16640)

This is a significant technological advance on the following points:
Clarity, color, performances and guarantees of industrial tonnages availability.

SR GreenPoxy 33 is an epoxy resin which has 35% of its molecular structure coming from plant origin.
This percentage is function of the carbon origin contained in the epoxy molecule.
The final rate of the mix bio-based carbon content will depend on the hardener choice.

SR GreenPoxy 33 / SZ 8525 epoxy system:
Clear laminate and final aspect.
High mechanical properties.
Good wetting out properties resulting in a low resin consumption.
Recommended cycle of 10 min at 100 °C
Mix bio-based carbon content of about 28 %.

Resin SR GreenPoxy 33:

Modified Epoxy matrix
Low viscosity


Profile:

High reactivity – short cycle times
Clear color
Very good adhesion on various material
Design for outdoor's composites equipment

Applications:

Wet lay-up
Pressure moulding
Hot process (90 – 120 °C)


Resin SR GreenPoxy 33:

Appearance		Viscous liquid
Color		Clear
Gardner color		3 maximum
Chemical nature		Epoxy resin. Reactions product between Alcohols and epichlorhydrine.
Storage		Can crystallize at low temperature or after a long storage. Shelf life : 2 years @ 18 - 25°C
Density (g/cm ³) ± 0.01	@ 20 °C	1.159
% bio-based Carbon content		34 - 36 %
Viscosities (m.Pas ± 20 %)	@ 15 °C	6 380
	@ 20 °C	3 240
	@ 25 °C	1 780
	@ 30 °C	1 040
	@ 40 °C	410
Refractive index (± 0.0005)	@ 25 °C	1.5562

Hardener SZ 8525:

Aspect / Color		Liquid / Light yellow
Gardner color		3 maximum
Reactivity levels		Standard
Density ± 0.01	@ 20 °C	0.94
Bio-based Carbon	%	0
Viscosities (m.Pas ± 20 %)	@ 20 °C	33
	@ 30 °C	25
	@ 40 °C	17
	@ 50 °C	11
	@ 60 °C	8
	@ 70 °C	6
	@ 80 °C	4
	@ 90 °C	3
Refractive index (± 0.0005)	@ 25 °C	1.4908


SR GreenPoxy 33 / SZ 8525 Mixes:

Mixing ratio:		
Quantity by weight		100 / 24
Quantity by volume		100 / 30
Mix % bio-based Carbon content		27– 29 %
Viscosities (m.Pas ± 20 %)	@ 20 °C	1 300
	@ 30 °C	620
	@ 40 °C	280
	@ 50 °C	110
	@ 60 °C	70
	@ 70 °C	50
	@ 80 °C	40
	@ 90 °C	30
	@ 100 °C	20


Reactivities on 500 g Mix **SR GreenPoxy 33 / SZ 8525**

Exothermic temperature (°C) :	
@ 20 °C	250
@ 30 °C	260
@ 40 °C	280
Time taken to achieve exotherm :	
@ 20 °C	1 hrs 35'
@ 30 °C	48'
@ 40 °C	33'
Time taken to reach 50 °C :	
@ 20 °C	1 hrs 15'
@ 30 °C	30'
@ 40 °C	11'


Pot life 500 g mix @ 20, 30 and 40 °C

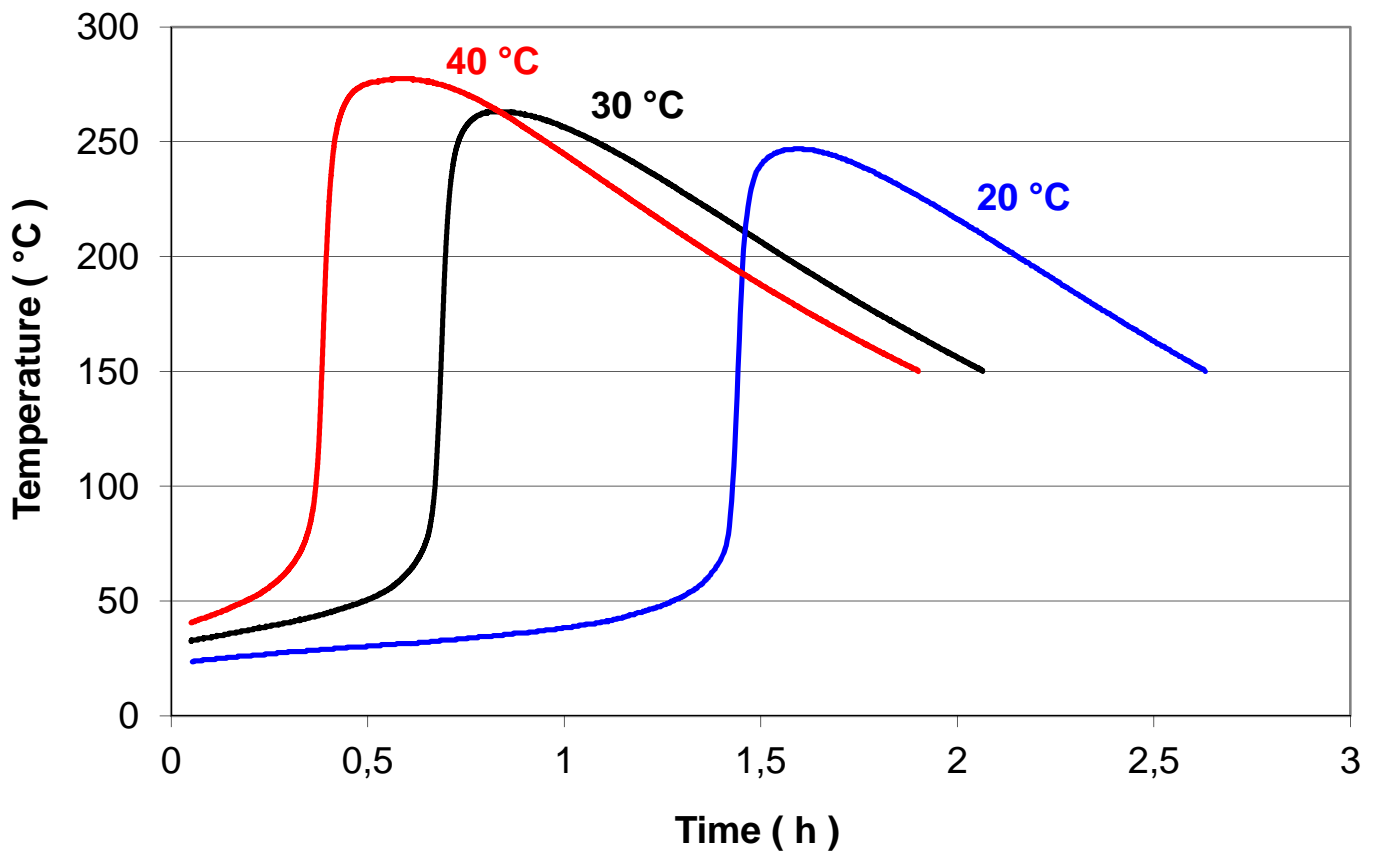


Reactivity – 1 mm film viscosity evolution with the temperature
SR GreenPoxy 33 / SZ 8525 @ 20, 30, 40 and 50 °C

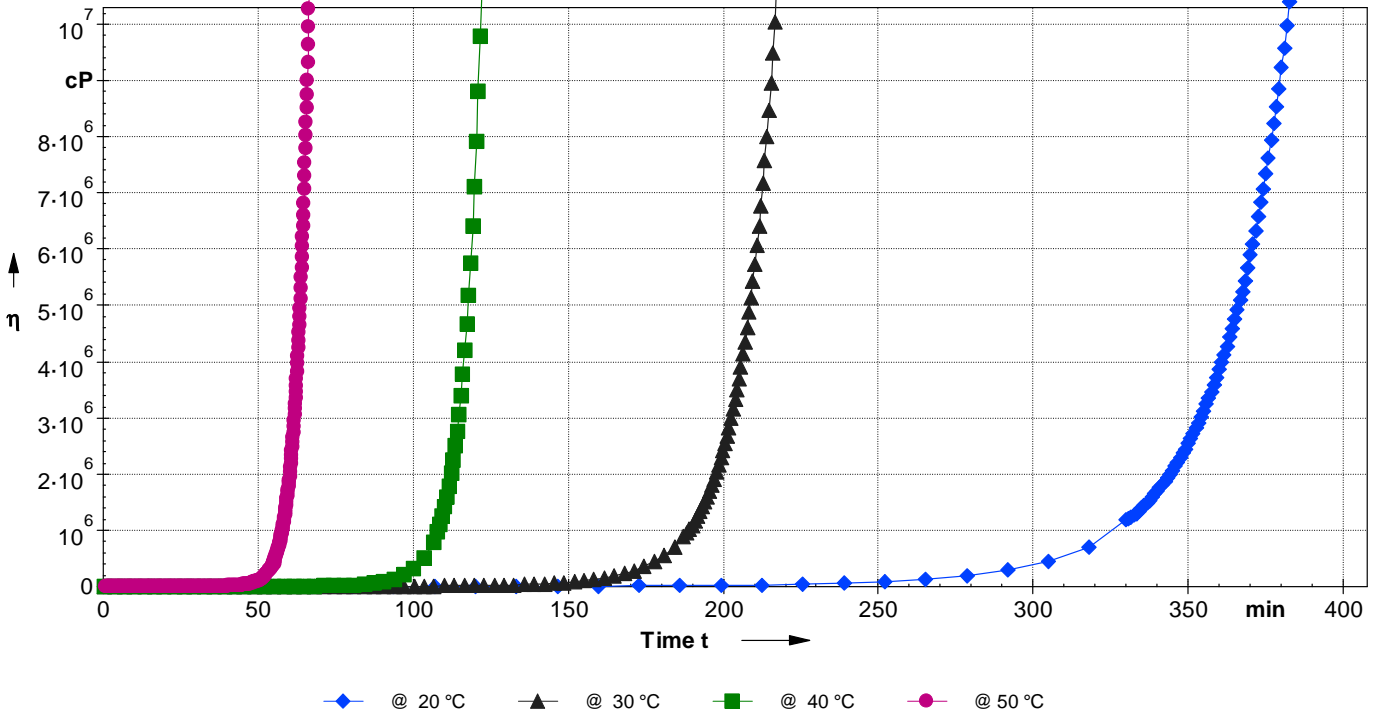

@ 50, 60, 70 °C (Hot process)

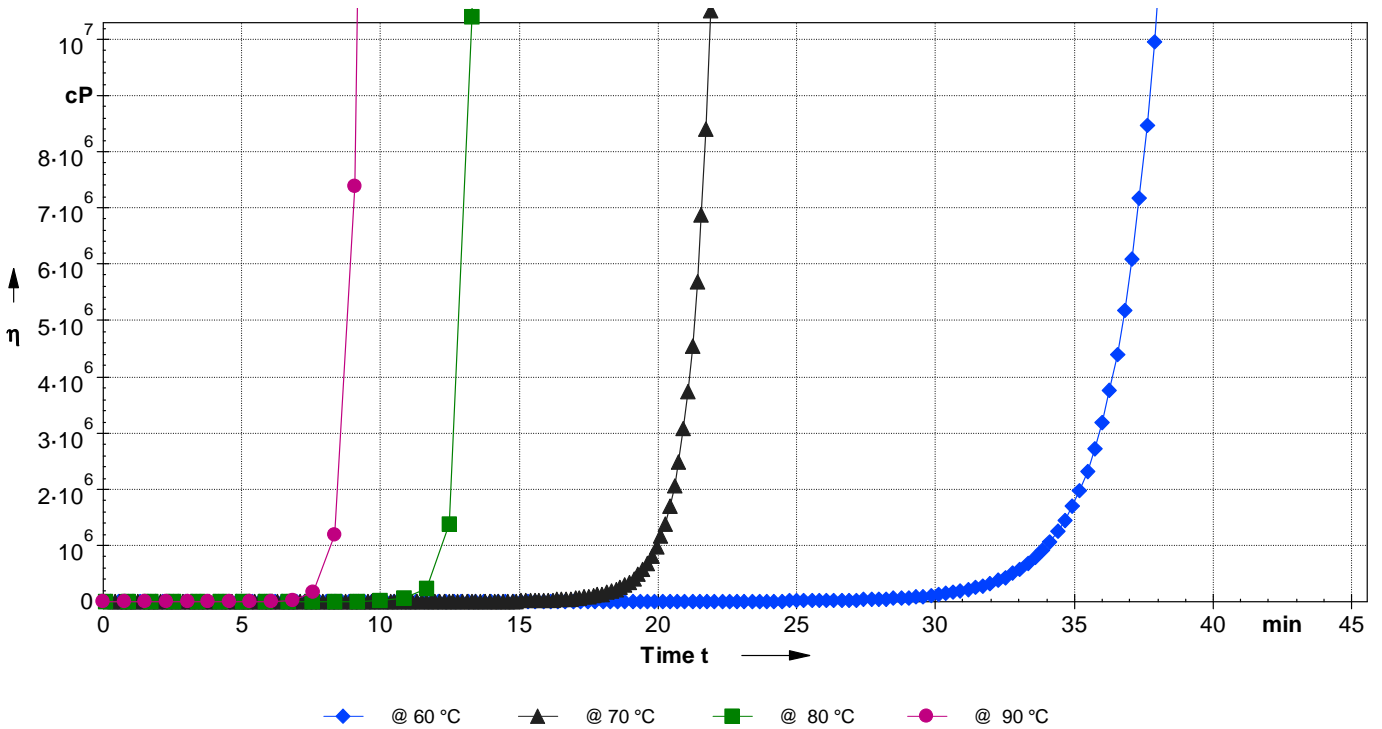

@ 70, 80, 90, 100 & 110 °C (Hot process)

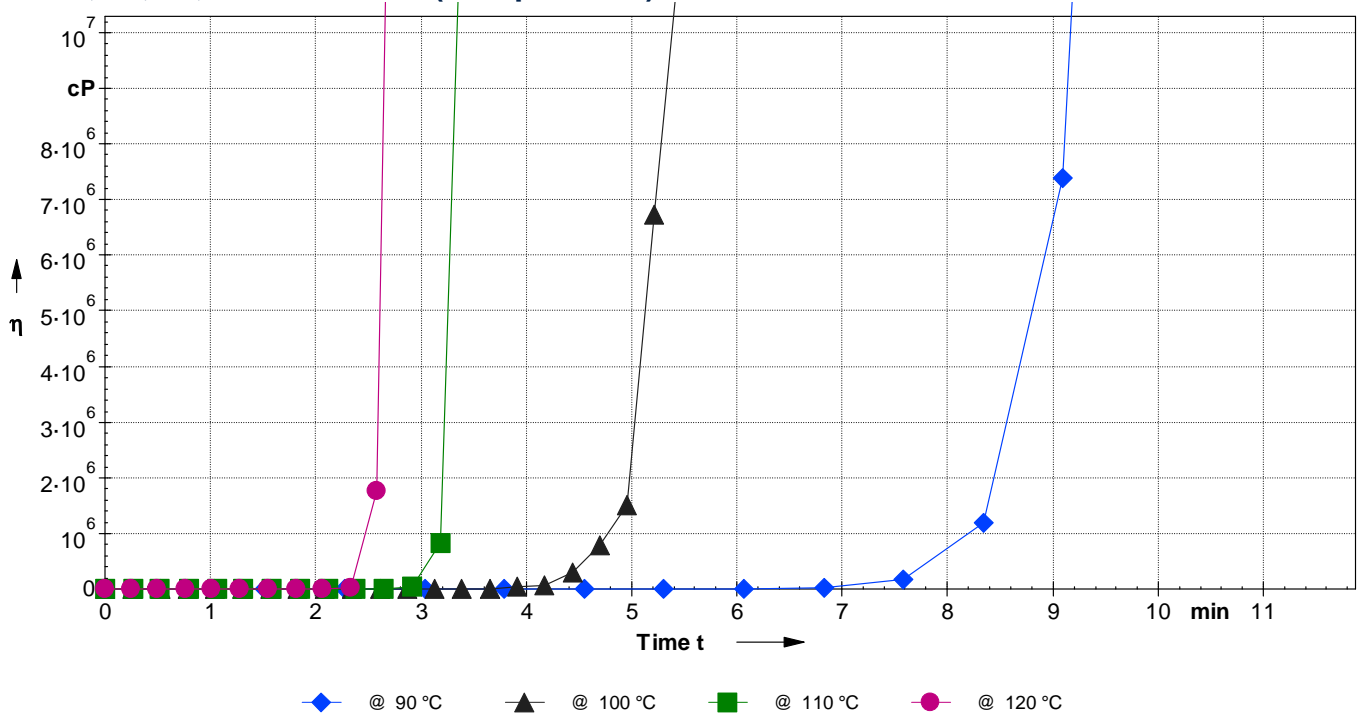

Time of Cure / hot process

Curing time	Tg onset DSC @ 80 °C	Tg onset DSC @ 90 °C	Tg onset DSC @ 100 °C	Tg onset DSC @ 110 °C	Tg onset DSC @ 120 °C
7'	/	/	/	/	87
8'	/	/	/	87	93
9'	/	/	/	93	100
10'	/	/	/	98	104
11'	/	/	87	100	107
12'	/	/	93	105	110
13'	/	/	100	107	112
14'	/	/	103	109	114
15'	/	87	105	112	116
17'	/	93	107	114	118
20'	/	100	112	117	120
25'	87	107	114	120	
35'	93	111	117		
45'	100	114	120		
1 h 10'	107	116			
2 h 15'	114	118			
2 h 45'	117	120			
4 h 30'	120				

/: not recommended, insufficient crosslinking

Data: without heating time to reach the curing temperature and without the time necessary to cooling of the mold.

Mechanical Properties of Pure casted mix Resin/hardener

Cure		Ambiant + 3 hrs 80°C	Ambiant + 1 hrs 100 °C	Ambiant + 30' 120 °C
Tension				
Modulus of elasticity	N/mm ²	3300	3000	3150
Maximum resistance	N/mm ²	71	80	80
Resistance at break		71	80	77
Elongation at max. resistance	%	2.8	5.1	5.6
Elongation at break	%	2.8	5.2	6.1
Flexion				
Modulus of elasticity	N/mm ²	3380	3150	3050
Maximum resistance	N/mm ²	128	119	115
Elongation at max. resistance	%	6.2	6.6	6.6
Shear strength	N/mm ²	57	55	53
Compression				
Compressive yield strength	N/mm ²	134	124	125
Offset compressive yield	%	10	11	10
Charpy impact strength				
Resilience	KJ/m ²	18	20	27
Glass Transition				
Tg 1 Onset	°C	117	120	120
Tg 1 Onset maximum	°C			114

Tests carried out on samples of pure cast resin, without prior degassing, between steel plates.

Measures undertaken according to the following norms:

Tension	:	Iso 527 - 2
Flexion	:	Iso 178
Charpy impact strength:		NF T 51-035
Shear Strength		ASTM D 732 - 93
Compressive		ISO 604
Water absorption:		Internal. Polymerisation according to cycle, machining, weighing, time spent in distilled water at 70 °C / 48 hours, weighing 1 hour after emerging,
Glass transition DSC :		ISO 11357-2 : 1999 -5°C to 180°C under nitrogen gaz Tg1 or Onset : 1st point at 20 °C/mn Tg1 maximum or Onset : second passage
Glass transition DTMA:		ISO 11357-1 - TG onset G' Temperature ramp 0°C to 180 °C @ 2°C/min ASTM D4065 - TG peak G''

Physical tests according standard ::

Gardner color:		NF EN ISO 4630 Visual method
Refractive index :		NF ISO 280
Viscosity:		NF EN ISO 3219 Rheometer 50 mm, shear 10s ⁻¹
Density:		NF EN ISO 2811-1 Pyknometer
Gel time :		Cross G' G'' / rheometer CP50 - Shear rate 10 s ⁻¹
GreenCarbon content:		ASTM D6866 or XP CEN/TS 16640 Avril 2014

LEGAL NOTES : The information given in writing or verbally, in the context of our technical assistance and our trials, do not engage our responsibility. They are given in good faith based on SICOMIN's current knowledge and experience of the products when properly stored, handled and applied under normal conditions in accordance with SICOMIN's recommendations. So, we advise the users of SICOMIN products, to check by some practical trials they are suitable for the envisaged processes and applications. The customer's storage, the use, the implementation and the transformation of the supplied products, are not under our control and your responsibility only will respond for it.

SICOMIN reserves the right to change the properties of its products. All technical data stated in this Product Data Sheet are based on laboratory tests. Actual measured data and tolerance may vary due to circumstances beyond our control.

If our responsibility should nevertheless be involved, it would be, for all the damages, limited to the value of the goods supplied by us and implement by the customer. We guaranty the non-reproachable quality of our products, in the general context of sales and delivery. Users must always refer to the most recent issue of the local Product Data Sheet for the product concerned, copies of which will be supplied on request.